

THERMAL PROPERTIES OF *Acacia mangium* CROSS LAMINATED TIMBER AND ITS GLUE LINES BONDED WITH TWO STRUCTURAL ADHESIVES

Norwahyuni Mohd Yusof¹,

<https://orcid.org/0000-0003-2549-437X>

Paridah Md Tahir^{1,*},

<https://orcid.org/0000-0002-2961-6031>

Lee Seng Hua^{1,*},

<https://orcid.org/0000-0001-6369-9902>

Fatimah Athiyah Sabaruddin¹,

<https://orcid.org/0000-0001-8513-7441>

Redzuan Mohammad Suffian James¹,

<https://orcid.org/0000-0001-8915-437X>

Mohd Asim Khan¹,

<https://orcid.org/0000-0001-9947-8730>

Lee Ching Hao¹,

<https://orcid.org/0000-0001-6347-9571>

Adlin Sabrina Muhammad Roseley²

<https://orcid.org/0000-0002-2616-3452>

ABSTRACT

The properties of cross laminated timber (CLT) can be affected by the type of adhesives used. The thermal properties of the adhesive that join the timber together is essential to determine the thermal endurance of the CLT product. In this study, two types of adhesives were used to join the cross laminated timber manufactured from *Acacia mangium* namely phenol resorcinol formaldehyde (PRF) and one component polyurethane (PUR). The thermal properties of the adhesives, *A. mangium* wood and the glue lines were determined via Thermogravimetric Analysis (TGA) and Dynamic Mechanical Analysis (DMA) tests. The TGA test showed that PRF adhesive had higher degradation temperature at 530 °C compared to PUR adhesive at 430 °C. Meanwhile, the PRF adhesive as a glue line in CLT also showed better thermal resistance where a higher amount of residue of 20,94 % was recorded at temperature up to 900 °C compared to PUR glue line with 18,26 % residue. The integrity of the CLT over temperature was determined via DMA test and the results showed that PRF adhesive as glue line had superior properties, indicating better interfacial bonding with the woods.

Keywords: *Acacia mangium*, cross laminated timber, dynamic mechanical analysis, interfacial bonding, one component polyurethane, phenol resorcinol formaldehyde.

¹Institute of Tropical Forestry and Forest Products, University Putra Malaysia, 43400 UPM Serdang, Selangor Darul Ehsan, Malaysia.

²Faculty of Forestry and Environment, University Putra Malaysia, 43400 UPM Serdang, Selangor Darul Ehsan, Malaysia.

*Corresponding authors: parida@upm.edu.my

Received: 21.10.2019 Accepted: 17.08.2020

INTRODUCTION

Cross-laminated timber (CLT) is a wood panel composite that joining at least three layers of solid-sawn timber by using an adhesive (Sutton *et al.* 2011). This material has been considered as high demand products that used as a constructional material for buildings. It enables a rapid installation for wall and floor structures that suitable for most finishes (Van De Kuilen *et al.* 2011). According to Dieste *et al.* (2019), CLT is a high value-added product compared to that of the other wood products. The mass production of CLT is formed in a similar way to “glue-laminated timber” beams using permanent adhesives which the limitations such as knots, checks, splits, warping and weathering can be removed to reduce variability and enhanced its structural properties. Almost all the studies of CLTs reported are constructed from softwood species such as spruce, larch, white fir, silver fir, Douglas fir, pine, and yellow poplar with density ranging from 350 kg/m³ to 700 kg/m³ (Engineering Toolbox 2004). For instance, Wang *et al.* (2018) fabricated CLT from spruce-pine-fir lumber pieces to study the effects of edge-gluing and gap size in the cross layers.

The rapid industrialization and increasing number of populations in the world causes the depleting of forest wealth at a rapid rate. The issue has urged the manufacturers to make use of fast grown plantation species for various timber applications (Shukla 2019). To relieve the pressure of the continuous extraction of logs from local natural forest, the establishment of plantation forests is a matter of utmost urgency. In 2005, a Forest Plantation Programme has been implemented by the Ministry of Plantation Industries and Commodities (MPIC) where a total of 375000 ha of forest plantation has been targeted to be developed at the end of 2020. The program aims to ensure the sustainability of the raw materials supply for the domestic timber industry. *Acacia* spp. (*mangium* /hybrid) and rubberwood (Timber Latex Clone) are the two major species out of nine selected species under this program.

A. mangium is one of the fast-growing and sustainable species for potentials timber production. It has a wood density ranging from 420 kg/m³ to 483 kg/m³ for green soaked volume and 500 kg/m³ to 600 kg/m³ in dry condition (Sarmin *et al.* 2014). In another study, the density of *A. mangium* was reported to fall within a range of 290 kg/m³ to 675 kg/m³. The density increases as the age of trees increased from 2 years to 20 years (Nordahlia *et al.* 2013). The density of wood is the best method to determine the quality of wood and correlated to its product's strength and shrinkage (Nugroho *et al.* 2012, Miranda *et al.* 2007, Lim *et al.* 2003). Wood is a renewable material and it has many applications. However, wood is easily degraded by sunlight, moisture and temperature due to the organic structure and the most important challenges of the components of wood are thermal decomposition of cellulose, lignin and hemicellulose at the low temperature (100 °C to 150°C) (Aydemir *et al.* 2016). Hence, wood has different degradation points and is highly dependent on their specific chemical compositions.

The selection of the adhesives to manufacture the CLT is very important as it needs to meet the characteristics and the application of the CLT itself. Polyurethane (PUR) adhesive glue is well known as a formaldehyde-free adhesive for exterior grade structure application for GLULAM and finger-joint in several European countries (Richter *et al.* 2006). Other than that, the thermal properties of the CLT are also very important but there is very limited information on this topic been reported. According to Asim *et al.* (2018), excellent thermal and fire-retardant behaviour of phenol resorcinol formaldehyde (PRF) adhesive glue allowed it to be used in building structural materials and automobile industry. Some studies have been conducted to compare the performance of PRF and PUR adhesives in CLT fabrication. Norwahyuni *et al.* (2019a) compared both PRF and PUR adhesive in bonding CLT from *A. mangium* wood. The authors reported that PRF adhesive performed better than that of PUR adhesive as it led to higher shear bond strength and wood failure percentage. In another study, Norwahyuni *et al.* (2019b) evaluated the mechanical and physical properties of *A. mangium* CLT bonded with PRF and PUR. The results revealed that the CLT bonded with PRF adhesive exhibited higher mechanical properties compared to that of the PUR-bonded CLT. Nevertheless, information on the thermal stability of PRF and PUR in CLT manufacturing is rather limited.

Therefore, the objective of this study is to evaluate the thermal properties of neat PRF and PUR adhesive, *A. mangium* wood as well as the glue line formed between wood and adhesive. The glue line formed between two adjacent layers of wood is important as it might impart some thermal resistance to the wood itself. Through thermal studies, the thermal degradation, weight loss, final residue, decomposition temperature of each component samples was assessed based on peak DTG curves, storage modulus, loss modulus and damping factor

of the samples.

MATERIALS AND METHODS

Manufacturing Cross Laminated Timber (CLT) species

Twenty-year-old *A. mangium* wood with a density of 673 kg/m³ and moisture content of 12 % ± 3 % was obtained from a local lumber mill located at Bukit Rambai, Melaka, Malaysia. The wood was sawn, trimmed and planed into 1000 mm long by 70 mm wide and 18,2 mm thick lumber. In this study, a 3-layer CLT of 1000 mm × 280 mm × 54,5 mm in size was produced by gluing three pieces of lumbers parallel and perpendicular to each other with edge bonding with 90° alternating transverse CLT layers. Boards were glued using two types of adhesive, namely phenol resorcinol formaldehyde (PRF) and one component polyurethane (PUR). Both types of adhesives were applied to the samples at a spreading rate of 250 g/m² within a short time to avoid possible oxidation and dimensional instability. The assemblies were then subjected to a pressure of 1,5 N/mm² at 30 °C for 90 minutes using a compressive machine. In the next stage, the laminated panels were conditioned at 65 % ± 5 % RH and 20 °C ± 2 °C for 2 weeks before cutting them into specimens for properties evaluation. Two types of adhesives were used in this study i.e., phenol resorcinol formaldehyde (PRF 1734 AkzoNobel) and one component polyurethane (1C-PUR or PUR, Jowapur 687,22). Hardener 2734 (commercial code) was also used in the preparation of PRF at a ratio of 100 to 25 parts by weight of PRF to hardener.

Characterization of the samples

Thermogravimetric Analysis (TGA)

Thermal stability of both PRF and PUR adhesives, *A. mangium* wood and glueline formed between wood and adhesives after pressing were characterized using Thermogravimetric analyzer (TGA Q 500 TA Instrument, USA) at Institute of Tropical Forestry and Forest Product (INTROP), University Putra Malaysia (UPM). In order to eliminate the effect of initial mass, 10 mg of sample was used for each experiment and placed in an alumina crucible. Non-isothermal TGA was conducted with the temperature raised from 10 °C to 900 °C with a rate of 10 °C/min in an oxygen atmosphere. The gas was purged at a constant flow rate of 30 mL/min. Three replications were used for every adhesive type tested. A total of 15 specimens (3 x (PRF and PUR adhesives + *A. mangium* wood + glueline formed by both adhesives)) were tested in this study.

Dynamic mechanical analysis (DMA)

Dynamic mechanical analysis (DMA) was executed to determine the viscoelastic behaviour of specimens from 30 °C to 150 °C with a heating rate of 5 °C/min and controlled sinusoidal strain. DMA test was performed by employing TA (DMA Q 800) instrument at INTROP, University Putra Malaysia, and operating in a three-point bending mode with 1 Hz oscillation frequency under controlled amplitude. The specimens having dimensions of 60 mm × 12 mm × 6 mm (l × w × t) were used for the testing. For DMA, only PRF and PUR gluelines were tested with three replications each. Therefore, a total of 6 specimens were evaluated.

RESULTS AND DISCUSSION

Thermogravimetric Analysis (TGA)

Heat resistance of a material is one of the most important criteria in any building construction. Since wood is combustible, the application of wood as building material becomes very limited. Thus, thermal evaluation is an essential method to determine the capability of the material to resist heat. In general, TGA is used to observe the material's thermal stability and degradation behaviour. TGA analysis on the neat adhesive (PRF and PUR), glue line between wood and the adhesive and *A. mangium* wood are demonstrated in Figure 1 and Table 1.

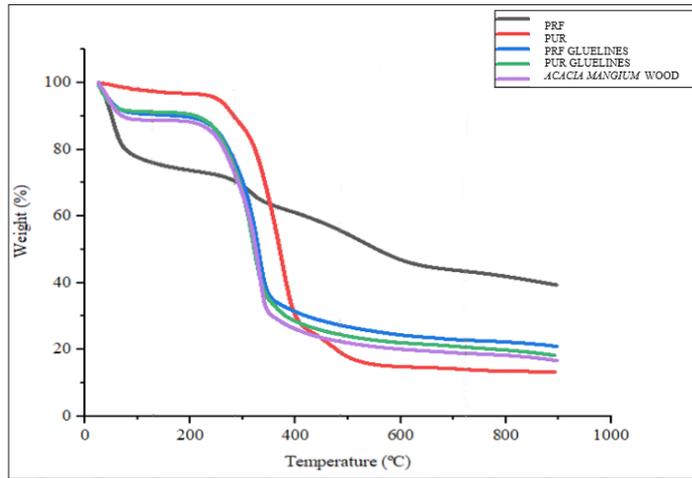


Figure 1: TGA curve of PRF, PUR, PRF glue line, PUR glue line and *A. mangium* wood.

During thermal degradation, drying of free water and major mass loss due to devolatilization and thermal debonding has been observed. All samples experienced a slight weight loss at temperature below 100 °C as shown in Figure 1 due to evaporation or dehydration of the water molecules (Sanyang *et al.* 2015, Nadirah *et al.* 2012, Johar *et al.* 2012). Significant weight loss (26,8 %) was observed for PRF adhesive glue at a temperature less than 100 °C due to the high amount of volatile free formaldehyde and phenol other than free water removal. This finding was aligned with the findings from previous studies done by Asim *et al.* (2018) and Liu *et al.* (2017). Both adhesives showed similar initial degradation temperature which occurred at 220 °C. However, PUR adhesive showed a higher weight loss of 74,40 % compared to PRF adhesive with the amount of weight loss of 47,92 % during the main degradation process. This finding could be attributed to the availability of the thermally unstable urethane bond in PUR adhesive that leads to rapid degradation (Lee *et al.* 2002).

Table 1: Thermogravimetric analysis (TGA) results.

Sample	Initial degradation temperature (°C)	Final degradation temperature (°C)	Weight loss (%)	Final residue at 900 °C (%)
PRF adhesive	220	530	47,92	39,37
PUR adhesive	220	430	74,40	13,24
<i>A. mangium</i> wood	140	380	72,38	16,72
PRF Glueline	140	360	65,43	20,94
PUR Glueline	130	420	72,57	18,26

Meanwhile, the weight loss of the *A. mangium* wood sample starts to occur between 30 °C up to about 130 °C, due to the hydrophilic nature of wood which resulted in high moisture absorption (Crespo *et al.* 2015, Angelini *et al.* 2009). The main degradation of *A. mangium* wood occurred at 140 °C up to 380 °C and this low thermal stability performance is attributed to the degradation of lignocellulosic components of the wood (hemicellulose, cellulose and lignin) (Manya *et al.* 2003). Higher lignocellulosic components caused a higher mass loss and lower initial degradation temperature (Lee *et al.* 2018, Lee *et al.* 2017). The first peak was attributed to the decomposition of hemicellulose, while the second peak can be attributed to the cellulose while degradation of lignin occurred at the wide temperature range and overlapping with the degradation of other components (Di Blasi 2008, Mészáros *et al.* 2004).

On the other hand, when both adhesives were applied to *A. mangium* wood (PRF glue line and PUR glue line), thermal degradation was expected to be similar to the degradation of pure *A. mangium* wood. This is because only

a small portion of the specimen's mass was being replaced by higher thermal stability adhesive glue. Although the use of adhesive does not improve the specimen's degradation temperature, the glue application slightly reduces the mass loss. PRF glue line specimen was reported to have a better integrity structure at temperature range up to 900 °C with 20,94 % of total residue compared to pure *A. mangium* wood and PUR glue line with the mass residue of 16,72 % and 18,26 %, respectively. This result could be attributed to good bonding properties between PRF adhesive and *A. mangium* wood compared to PUR adhesive.

Derivative thermo-gravimetric (DTG) analysis of both PRF and PUR adhesives, *A. mangium* wood and glue-line of both PRF and PUR are shown in Figure 2. DTG analysis is used to study the rate of degradation of the materials up to a certain temperature (Ridzuan *et al.* 2016). Three peaks were observed for all specimens which are below 100 °C, 280 °C to 380 °C and 420 °C to 520 °C. A low first degradation peak responsible for free water removal except for PRF adhesive glue. A maximum decomposition rate at 4,83 %/min for PRF was observed due to the presence of hydroxyl molecule in PRF adhesive glue (Asim *et al.* 2016). All specimens demonstrate the maximum rate of weight losses in the second peak except PRF adhesive glue. *A. mangium* wood showed a higher DTG value at the second peak among all the samples. Meanwhile, the application of adhesive glues (PRF and PUR) on *A. mangium* wood seems to reduce the rate of weight loss as part of the specimen's mass replaced by higher thermal stability materials. No significant changes showed at the third region of DTG peaks for all samples.

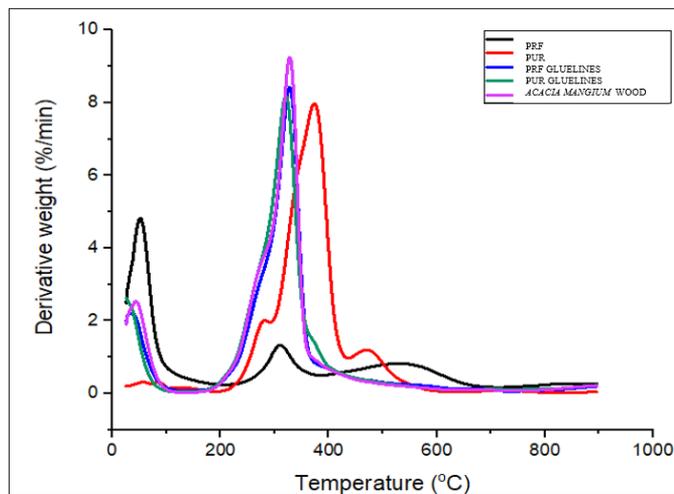


Figure 2: DTG curve of PRF, PUR, PRF glue-line, PUR glue-line and *A. mangium* wood.

Dynamic mechanical analysis (DMA)

DMA is one of the most functional analysis to investigate the morphological and viscoelastic properties of a material. It helps to analyse some other parameters such as primary relaxations, storage or loss compliance, dynamic fragility, cross-linking density, creep compliance and dynamic viscosity (Ornaghi *et al.* 2012, Pistor *et al.* 2012, Joseph *et al.* 2010, Qazvini and Mohammadi 2005). It is a technique where small deformation is applied in a cyclic manner.

In this section, only the glue lines formed by PRF and PUR adhesives were tested and discussed. Figure 3 illustrates the storage modulus of PRF and PUR adhesive glue lines of CLT made by *A. mangium* wood. According to Saba *et al.* (2016a), there are three regions found for viscoelastic materials, namely glassy region, transition region and rubbery region. High storage modulus value indicated the glassy region where the components are in tightly packed and drop as it reached the glass transition temperature (T_g). This is because slipping of polymer chain above T_g reduces its modulus and performances. As the temperature increase, the component tends to increase in mobility correspond to rubbery state transition (Jawaid and Khalil 2011, Hameed *et al.* 2007, Jacob *et al.* 2006). The investigation of various storage modulus with a temperature of CLT was found to decrease with temperature increment. At low temperature, the storage modulus PRF glue line is higher but close to PUR glue line, suggesting that PRF glue line has better stiffness but lower mobility and flexibility (Chartoff *et al.* 2009). This finding was synchronized with

TGA results reported in the above section where PRF glue line has better interfacial bonding between wood and PRF glue. Besides, a sudden drop in storage modulus at about 100 °C for both glue lines represents glass transition temperature, T_g zone.

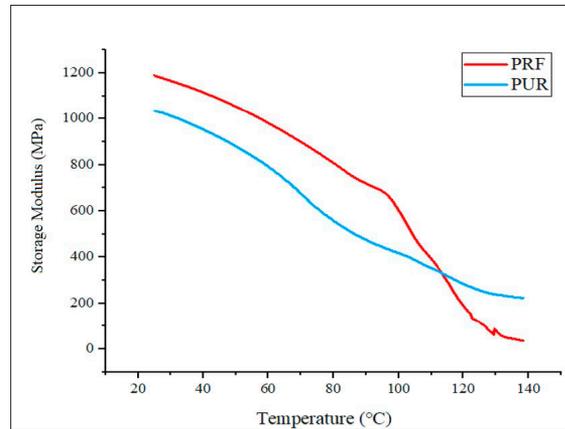


Figure 3: Storage Modulus of PRF glue line and PUR glue line.

Meanwhile, the loss modulus measurement is carried out on the energy dissipation response under the reciprocal deformation of a material (Jawaid *et al.* 2012). The loss modulus of PRF and PUR adhesive glue line of CLT made by *A. mangium* wood are illustrated in Figure 4. Both curves at maximum value indicates maximum dissipation of mechanical energy at lower temperature and decreased dramatically at higher temperature due to the free movement of polymer (Saba *et al.* 2016b). From Figure 4, both glue lines demonstrated a wide peak at 60 °C to 100 °C and the T_g observed for PRF glue line is slightly lower than PUR glue line. This is because the inter-molecular friction in the PRF glue line was higher and increases the dissipation of energy within CLT (Hameed *et al.* 2007). PRF glue line resulted in a higher loss of modulus due to the increased amount of energy needed to disentangle a better interfacial bonding.

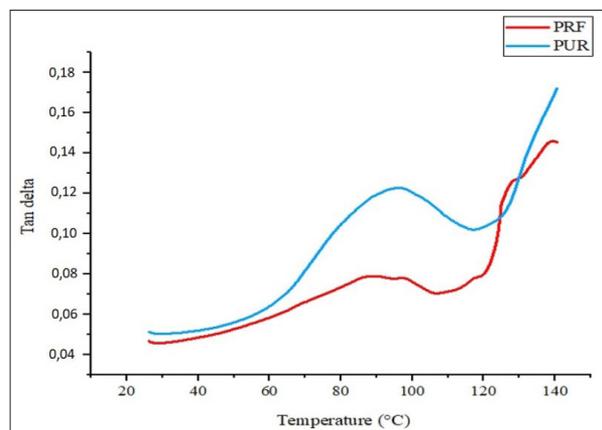


Figure 4: Loss Modulus of PRF glue line and PUR glue line.

Damping factor determines the ability of material on absorbing energy at a range of temperature or frequency. Damping is important when designing advanced structural especially when vibration and noise control involved. Besides, it is used to study the fatigue life and impact resistance of structural materials and monitor damage (Melo and Radford 2005). Figure 5 depicts the damping factor curve trend of the CLT for both types of glue lines with the temperature at frequency of 1 Hz. At temperature below T_g , low $\tan \delta$ corresponds to close pack molecular structure. Whilst the temperature sweep, the $\tan \delta$ increased indicate both glue lines become more viscous. A wide area of $\tan \delta$ peak for PUR glue line observed in this test reflecting higher dynamic fragility, due to poor interfacial bonding between adhesive and wood. On the other hand, the lower $\tan \delta$ peak of PRF glue line showed a good inter-

terfacial adhesion similar to the results of storage modulus (Jawaid and Khalil 2011). From the $\tan \delta$ curve in Figure 5, T_g of PRF glue line was also observed to be slightly lower than PUR glue line. George *et al.* (2003) evaluated two commercial PRF and PUR adhesives using thermomechanical analysis (TMA) and found that wood joints bonded with PUR exhibited a significant temperature-dependant creep. The finding suggested that PUR is not suitable for structural application. As in this study, similar conclusion can be drawn, where PUR is an inferior adhesive compared to PRF in the manufacturing of CLT.

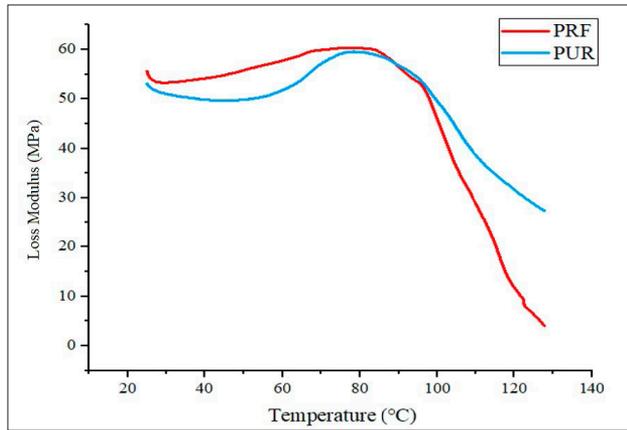


Figure 5: Damping Factor of PRF glue line and PUR glue line.

CONCLUSIONS

In this study, thermogravimetric analysis was performed on both neat PRF and PUR adhesives, *A. mangium* wood, as well as glue lines of both PRF and PUR, formed after CLT fabrication process. On the other hand, dynamic mechanical analysis was conducted to characterize the PRF and PUR glue lines. Generally, it was found that PRF adhesive glue was more thermally stable than PUR adhesive glue, with a higher percentage of residue in TGA test. Both adhesive glues start the degradation at the same temperature of 220 °C but PRF adhesive showed higher degradation temperature at 530 °C at the second stage with a lower percentage of weight loss of 47,92 %. As expected, *A. mangium* wood specimen has the lowest thermal properties due to the low thermal stability of hemicellulose. The application of adhesives glue on *A. mangium* did improve the thermal stability of the wood by reducing weight loss during the degradation process. In comparison, PRF glue line has better thermal stability compared to that PUR glue line as indicated by its higher residue at temperature up to 900 °C.

In DMA, the storage modulus of PRF glue line is higher but close to PUR glue line, suggesting that PRF glue line has better stiffness but lower mobility and flexibility. A sudden drop in storage modulus at about 100 °C for both glue lines, indicating glass transition temperature, T_g and major main chain slipping were found. The T_g of PRF glue line observed from $\tan \delta$ and loss modulus curve was slightly lower than that of PUR glue line. Besides, PRF glue line resulted in a higher loss of modulus due the increased amount of energy needed to disentangle a better interfacial bonding. A similar trend was also found in loss modulus and $\tan \delta$ curves. Based on results obtained, it can be concluded that PRF adhesive is a better binding agent for *A. mangium* wood in the manufacturing of CLT as it resulted in better interfacial bonding and a promising thermal performance at higher working temperature compared to PUR.

ACKNOWLEDGEMENTS

This study was financially supported by the Higher Institution Centre of Excellence (HiCoE) for the project titled “Development of aeronautic composites made from biophenolic microspheres from plant sourced” (Code: 6369109) granted to Paridah Md Tahir. The authors also would like to extend their gratitude for the facilities support from HLM Wood Products Sdn. Bhd.

REFERENCES

- Angelini, L.G.; Ceccarini, L.; Nassi O Di Nasso, N.; Bonari, E. 2009.** Comparison of *Arundo Donax* L. and *Miscanthus x Giganteus* in a long-term field experiment in central Italy: analysis of productive characteristics and energy balance. *Biomass Bioenerg* 33(4): 635-643. <https://doi.org/10.1016/j.biombioe.2008.10.005>
- Asim, M.; Jawaid, M.; Abdan, K.; Ishak, M.R. 2016.** Effect of alkali and silane treatments on mechanical and fibre-matrix bond strength of kenaf and pineapple leaf fibres. *J Bionic Eng* 13(3): 426-435. [https://doi.org/10.1016/S1672-6529\(16\)60315-3](https://doi.org/10.1016/S1672-6529(16)60315-3)
- Asim, M.; Jawaid, M.; Nasir, M.; Saba, N. 2018.** Effect of fiber loadings and treatment on dynamic mechanical, thermal and flammability properties of pineapple leaf fiber and kenaf phenolic composites. *J Renew Mater* 6(4): 383-393. <https://doi.org/10.7569/JRM.2017.634162>
- Aydemir, D.; Civi, B.; Alsan, M.; Can, A.; Sivrikaya, H.; Gunduz, G.; Wang, A. 2016.** Mechanical, morphological and thermal properties of nano-boron nitride treated wood materials. *Maderas-Cienc Tecnol* 18(1): 19-32. <http://dx.doi.org/10.4067/S0718-221X2016005000003>
- Crespo, Y.A.; Naranjo, R.A.; Burgos, J.C.V.; Sanchez, C.G.; Sanchez, E.M. 2015.** Thermogravimetric analysis of thermal and kinetic behavior of *Acacia mangium* wood. *Wood Fiber Sci* 47(4): 327-335. <http://wfs.swst.org/index.php/wfs/article/view/2363>
- Chartoff, R.P.; Menczel, J.D.; Dillman, S.H. 2009.** Dynamic Mechanical Analysis (DMA). In *Thermal Analysis of Polymers: Fundamentals and Applications*, Menczel, J.D.; Bruce Prime, R. (Eds.). John Wiley and Sons: New Jersey, USA. pp. 387-495. <https://doi.org/10.1002/9780470423837.ch5>
- Di Blasi, C. 2008.** Modeling chemical and physical processes of wood and biomass pyrolysis. *Prog Energy Combust Sci* 34(1): 47-90. <http://doi.org/10.1016/j.peccs.2006.12.001>
- Dieste, A.; Cabrera, M.N.; Clavijo, L.; Cassell, N. 2019.** Analysis of wood products from an added value perspective: the Uruguayan forestry case. *Maderas-Cienc Tecnol* 21(3): 305 – 316. <http://dx.doi.org/10.4067/S0718-221X2019005000303>
- Engineering Toolbox. 2004.** Density of various wood species. https://www.engineeringtoolbox.com/wood-density-d_40.html
- George, B.; Simon, C.; Properzi, M.; Pizzi, A.; Elbez, G. 2003.** Comparative creep characteristics of structural glulam wood adhesives. *Holz Roh Werkst* 61(1): 79-80. <https://doi.org/10.1007/s00107-002-0348-3>
- Hameed, N.; Sreekumar, P.A.; Francis, B.; Yang, W.; Thomas, S. 2007.** Morphology, dynamic mechanical and thermal studies on poly (styrene-co-acrylonitrile) modified epoxy resin/glass fibre composites. *Compos Part A Appl Sci Manuf* 38(12): 2422-2432. <https://doi.org/10.1016/j.compositesa.2007.08.009>
- Jacob, M.; Francis, B.; Varughese, K.; Thomas, S. 2006.** The effect of silane coupling agents on the viscoelastic properties of rubber biocomposites. *Macromol Mater Eng* 291(9): 1119-1126. <https://doi.org/10.1002/mame.200600171>
- Jawaid, M.; Abdul Khalil, H.P.S.; Alattas, O. 2012.** Woven hybrid biocomposites: dynamic mechanical and thermal properties. *Compos Part A Appl Sci Manuf* 43(2): 288-293. <https://doi.org/10.1016/j.compositesa.2011.11.001>
- Jawaid, M.; Abdul Khalil, H.P.S. 2011.** Effect of layering pattern on the dynamic mechanical properties and thermal degradation of oil palm-jute fibers reinforced epoxy hybrid composite. *BioResources* 6(3): 2309-2322. https://ojs.cnr.ncsu.edu/index.php/BioRes/article/view/BioRes_06_3_2309_Jawaid_A_Layering_Pattern_DMA_Epoxy_Hybrid_Composites

- Johar, N.; Ahmad, I.; Dufresne, A. 2012.** Extraction, preparation and characterization of cellulose fibres and nanocrystals from rice husk. *Ind Crops Prod* 37(1): 93-99. <https://doi.org/10.1016/j.indcrop.2011.12.016>
- Joseph, S.; Appukuttan, S.P.; Kenny, J.M.; Puglia, D.; Thomas, S.; Joseph, K. 2010.** Dynamic Mechanical Properties of oil palm microfibril-reinforced natural rubber composites. *J Appl Polym Sci* 117(3): 1298-1308. <https://doi.org/10.1002/app.30960>
- Lee, C.H.; Sapuan, S.M.; Hassan, M.R. 2018.** Thermal analysis of kenaf fiber reinforced floreon biocomposites with magnesium hydroxide flame retardant filler. *Polym Compos* 39(3): 869-875. <https://doi.org/10.1002/pc.24010>
- Lee, C.H.; Sapuan, S.M.; Hassan, M.R. 2017.** Mechanical and thermal properties of kenaf fiber reinforced polypropylene/magnesium hydroxide composites. *J Eng Fiber Fabr* 12(2): 50-58. <https://doi.org/10.1177/155892501701200206>
- Lee, S.H.; Teramoto, Y.; Shiraishi, N. 2002.** Biodegradable polyurethane foam from liquefied waste paper and its thermal stability, biodegradability, and genotoxicity. *J Appl Polym Sci* 83(7): 1482-1489. <https://doi.org/10.1002/app.10039>
- Lim, S.C.; Gan, K.S.; Choo, K.T. 2003.** The characteristics, properties and uses of plantation timbers; rubberwood and Acacia mangium. *Timber Technology Bulletin* 26: 1-10. <https://info.frim.gov.my/infocenter/booksonline/ttb/TTBno26.pdf>
- Liu, J.; Chen, R.Q.; Xu, Y.Z.; Wang, C.P.; Chu, F.X. 2017.** Resorcinol in high solid phenol-formaldehyde resins for foams production. *J Appl Polym Sci* 134(22): 44881. <https://doi.org/10.1002/app.44881>
- Manya, J.J.; Velo, E.; Puigjaner, L. 2003.** Kinetics of biomass pyrolysis: a reformulated three-parallel-reactions model. *Ind Eng Chem Res* 42(3): 434-441. <https://doi.org/10.1021/ie020218p>
- Melo, J.D.; Radford, D.W. 2005.** Time and temperature dependence of the viscoelastic properties of cfrp by dynamic mechanical analysis. *Compos Struct* 70(2): 240-253. <https://doi.org/10.1016/j.compstruct.2004.08.025>
- Mészáros, E.; Várhegyi, G.; Jakab, E.; Marosvölgyi, B. 2004.** Thermogravimetric and reaction kinetic analysis of biomass samples from an energy plantation. *Energ Fuel* 18(2): 497-507. <https://doi.org/10.1021/ef034030>
- Miranda, I.M.; Almeida, H.; Pereira, H. 2007.** Influence of provenance, subspecies, and site on wood density in *Eucalyptus globulus* Labill. *Wood Fiber Sci* 33(1): 9-15. <https://wfs.swst.org/index.php/wfs/article/view/66>
- Nadirah, W.O.; Jawaid, M.; Al Masri, A.A.; Abdul Khalil, H.P.S.; Suhaily, S.S.; Mohamed, A.R. 2012.** Cell wall morphology, chemical and thermal analysis of cultivated pineapple leaf fibres for industrial applications. *J Polym Environ* 20(2): 404-411. <https://doi.org/10.1007/s10924-011-0380-7>
- Nordahlia, A.S.; Hamdan, H.; Anwar, U.M.K. 2013.** Wood properties of selected plantation species: *Khaya ivorensis* (african mahogany), *Azadirachta excelsa* (sentang), *Endospermum malaccense* (sesendok) and *Acacia mangium*. *Timber Technology Bulletin* 51: 1-4. <https://info.frim.gov.my/infocenter/booksonline/ttb/TTB51.pdf>
- Norwahyuni, M.Y.; Tahir, P.M.; Roseley, A.S.M.; Lee, S.H.; Halip, J.A.; James, R.M.S.; Ashaari, Z. 2019a.** Bond integrity of cross laminated timber from *Acacia mangium* wood as affected by adhesive types, pressing pressures and loading direction. *Int J Adhes Adhes* 94: 24-28. <https://doi.org/10.1016/j.ijadhadh.2019.05.010>
- Norwahyuni, M.Y.; Tahir, P.M.; Lee, S.H.; Khan, M.A.; James, R.M.S. 2019b.** Mechanical and physical properties of Cross-Laminated Timber made from *Acacia mangium* wood as function of adhesive types. *J Wood Sci* 65(1): 20. <https://doi.org/10.1186/s10086-019-1799-z>
- Nugroho, W.D.; Marsoem, S.N.; Yasue, K.; Fujiwara, T.; Nakajima, T.; Hayakawa, M.; Nakaba, S.; Yamagishi, Y.; Jin, H.; Kubo, T.; Funada, R. 2012.** Radial variations in the anatomical characteristics and

density of the wood of *Acacia mangium* of five different provenances in Indonesia. *J Wood Sci* 58(3): 185-194. <https://doi.org/10.1007/s10086-011-1236-4>

Ornaghi, H.L.; Pistor, V.; Zattera, A.J. 2012. Effect of the epoxy-cyclohexyl polyhedral oligomeric silsesquioxane content on the dynamic fragility of an epoxy resin. *J Non Cryst Solids* 358(2): 427-432. <https://doi.org/10.1016/j.jnoncrsol.2011.10.014>

Pistor, V.; Ornaghi, F.G.; Ornaghi, H.L.; Zattera, A.J. 2012. Dynamic mechanical characterization of epoxy/epoxycyclohexyl-POSS nanocomposites. *J Mater Sci Eng A* 532: 339-345. <https://doi.org/10.1016/j.msea.2011.10.100>

Qazvini, N.T.; Mohammadi, N. 2005. Dynamic Mechanical Analysis of segmental relaxation in unsaturated polyester resin networks: effect of styrene content. *Polymer* 46(21): 9088-9096. <https://doi.org/10.1016/j.polymer.2005.06.118>

Ridzuan, M.J.M.; Majid, M.A.; Afendi, M.; Mazlee, M.N.; Gibson, A.G. 2016. Thermal behaviour and dynamic mechanical analysis of pennisetum purpureum/glass-reinforced epoxy hybrid composites. *Compos Struct* 152: 850-859. <https://doi.org/10.1016/j.compstruct.2016.06.026>

Richter, K.; Pizzi, A.; Despres, A. 2006. Thermal stability of structural one-component polyurethane adhesives for wood-structure-property relationship. *J Appl Sci* 102(6): 5698-5707. <https://doi.org/10.1002/app.25084>

Saba, N.; Jawaid, M.; Alothman, O.Y.; Paridah, M. T. 2016a. A review on dynamic mechanical properties of natural fibre reinforced polymer composites. *Constr Builds Mater* 106(1): 149-159. <https://doi.org/10.1016/j.conbuildmat.2015.12.075>

Saba, N.; Paridah, M.T.; Abdan, K.; Ibrahim, N.A. 2016b. Dynamic Mechanical Properties of oil palm nano filler/kenaf/epoxy hybrid nanocomposites. *Constr Builds Mater* 124: 133-138. <https://doi.org/10.1016/j.conbuildmat.2016.07.059>

Sarmin, S. N.; Rosman, N.; Kasim, J.; Zakaria, S. A. K. Y. 2014. Effects of Different Resin Content and Densities on Some Properties of Hybrid Wood Sawdust-Acacia mangium Composites. In Proceedings of the International Conference on Science, Technology and Social Sciences (ICSTSS) 2012. pp. 485-491. Springer: Singapore. https://doi.org/10.1007/978-981-287-077-3_57

Sanyang, M.L.; Sapuan, S.M.; Jawaid, M.; Ishak, M.R.; Sahari, J. 2015. Effect of plasticizer type and concentration on tensile, thermal and barrier properties of biodegradable films based on sugar palm (*Arenga pinnata*) starch. *Polymer* 7(6): 1106-1124. <https://doi.org/10.3390/polym7061106>

Shukla, S.R. 2019. Evaluation of dimensional stability, surface roughness, colour, flexural properties and decay resistance of thermally modified *Acacia auriculiformis*. *Maderas-Cienc Tecnol* 21(4): 433-446. <http://dx.doi.org/10.4067/S0718-221X2019005000401>

Sutton, A.; Black, D.; Walker, P. 2011. Cross-Laminated Timber: an introduction to low-impact building materials. IHS BRE Press: Watford, UK.

Van De Kuilen, J.W.G.; Ceccotti, A.; Xia, Z.; He, M. 2011. Very tall wooden buildings with cross laminated timber selection and/or peer-review under responsibility. *Procedia Eng* 14: 1621-1628. <https://doi.org/10.1016/j.proeng.2011.07.204>

Wang, Z.; Zhou, J.; Dong, W.; Yao, Y.; Gong, M. 2018. Influence of technical characteristics on the rolling shear properties of cross laminated timber by modified planar shear tests. *Maderas-Cienc Tecnol* 20(3): 469-478. <http://dx.doi.org/10.4067/S0718-221X2018005031601>