

## CHEMICAL CHANGES OF HEAT TREATED PINE AND EUCALYPT WOOD MONITORED BY FTIR

B. Esteves<sup>1\*</sup>, A. Velez Marques<sup>2</sup>, I. Domingos<sup>1</sup>, H. Pereira<sup>3</sup>

### ABSTRACT

A hardwood, *Eucalyptus globulus* Labill., and a softwood *Pinus pinaster* Aiton., were heat treated at temperatures between 170 and 210°C in an oven and in an autoclave. The samples were pre-extracted with dichloromethane, ethanol and water and ground prior to Fourier Transform Infrared (FTIR) spectroscopic analysis.

The heat treatment caused significant changes in the chemical composition and structure of wood, in lignin and polysaccharides. Hemicelluloses were the first to degrade as proved by the initial decrease of the 1730 cm<sup>-1</sup> peak due to the breaking of acetyl groups in xylan. Hardwood lignin changed more than softwood lignin, with a shift of maximum absorption from 1505 cm<sup>-1</sup> to approximately 1512 cm<sup>-1</sup> due to decrease of methoxyl groups, loss of syringyl units or breaking of aliphatic side-chains. The macromolecular structure becomes more condensed and there is a clear increase of non-conjugated (1740 cm<sup>-1</sup>) in relation to conjugated groups (1650 cm<sup>-1</sup>). However, the changes induced by the thermal treatment are difficult to monitor by FTIR spectroscopy due to the different chemical reactions occurring simultaneously.

**Keywords:** *Eucalyptus globulus*, FTIR, Heat treatment, *Pinus pinaster*

### INTRODUCTION

Heat treatment is one of the processes for modifying the wood with greater commercial success. There are different treatments: the Thermowood® process, originated in Finland, uses steam (Viitanen *et al.* 1994), the Plato® process, developed in the Netherlands, uses a combination of steam and heated air (Tjeerdsma *et al.* 1998), the Retiwood® process, of French origin, uses an inert gas (Dirol and Guyonnet 1993), the OHT® from Germany, uses hot oil (Sailer *et al.* 2000) and the Perdure® process, initially developed in France but later sold to a company from Canada (Kocaefe *et al.* 2008a) uses steam.

Heat treatments lower the equilibrium moisture content of wood (Jämsä and Viitaniemi 2001, Wang and Cooper 2005, Esteves *et al.* 2007a, Esteves *et al.* 2007b, Esteves *et al.* 2008a), increase its dimensional stability (Viitaniemi *et al.* 1997, Yildiz 2002, Wang and Cooper 2005, Esteves *et al.* 2007a, Esteves *et al.* 2007b), and increase its durability (Dirol and Guyonnet 1993, Kamdem *et al.* 2002) and its darkness (Mitsui *et al.* 2001, Bekhta and Niemz 2003, Esteves *et al.* 2008c). The main disadvantage of these heat processes is the reduction of the wood mechanical strength properties, such as static and dynamic bending strength (Yildiz 2002, Esteves *et al.* 2007b) and resistance to compression (Unsal and Ayrilmis 2005).

<sup>1</sup> Centre of Studies in Education, Technologies and Health, School of Technology of Viseu, Polytechnic Institute of Viseu, Campus Politécnico Repeses, 3504-510, Viseu, Portugal

<sup>2</sup> Research Centre for Chemical Engineering and Biotechnology (CIEQB), Superior Institute of Engineering of Lisbon, Lisbon, Portugal

<sup>3</sup> Forest Research Centre, School of Agronomy, Technical University of Lisbon, Lisbon, Portugal

\*Corresponding author: bruno@demad.estv.ipv.pt

Received: 02. 02. 2012 Accepted: 11.11. 2012.

There are chemical changes in the wood during heating. They start by deacetylation of hemicelluloses followed by depolymerization catalysed by the released acetic acid (Tjeerdsma *et al.* 1998, Sivonen *et al.* 2002, Nuopponen *et al.* 2004). Simultaneously hemicelluloses undergo dehydration with the decrease of hydroxyl groups (Weiland and Guyonnet 2003). In accordance with Esteves *et al.* (2008b) hemicelluloses are affected first, followed by cellulose and lignin.

FTIR is widely used in quantitative and qualitative analysis of wood because of its capacity to give information on the presence of functional groups, on composition and on some specific structural features.

The main objective of this paper was to track the chemical changes occurring along the heat treatment (two different treatments, one with hot air and the other with steam) of a hardwood (*Eucalyptus globulus*) and a softwood (*Pinus pinaster*) by FTIR.

## MATERIAL AND METHODS

Two of the most important tree species in Portugal were tested: the hardwood *Eucalyptus globulus* Labill. and the softwood *Pinus pinaster* Aiton. The pine samples were taken from the sapwood of a 40 year old tree from the Portuguese region of Águeda. For the eucalypt samples only heartwood was used from a tree with approximately 1 m in diameter, from the same region. The samples were treated in an oven and in an autoclave under several operating conditions.

Cubic samples were prepared, with 40 mm edge, free from knots, resin canals or other singularities, with faces parallel to radial, tangential and longitudinal directions. The samples were stabilized during three weeks in a room conditioned at 50% relative humidity and 20°C. The equilibrium moisture content and the mass of all samples were determined.

### **Oven heat treatments**


The stabilized samples were treated in a Selecta 125 litre oven without forced convection but with an outlet for gases exhaustion. The trials were conducted in the presence of air during 2, 6, 12 and 24 h, at 170°C and 180°C. The time to reach the treatment temperature was one hour. Four samples were used in each test, making up a total of 32 samples for each species. At the end of the heat treatment all samples remained for one hour in a desiccator and were weighted. The mass loss was determined for each sample in relation to its initial dry mass in accordance with:

$$\text{Mass loss (\%)} = (\text{dry mass} - \text{treated mass}) / \text{dry mass} * 100$$

where the dry mass is the mass of the specimen without treatment, and the treated mass corresponds to the dry mass of the specimen after heat treatment.

### **Autoclave heat treatment**

The heat treatment in autoclave was carried out in an industrial prototype (Figure 1), used for the production of expanded cork agglomerates, installed in an industrial plant of the Amorim Group located in Silves, Portugal.

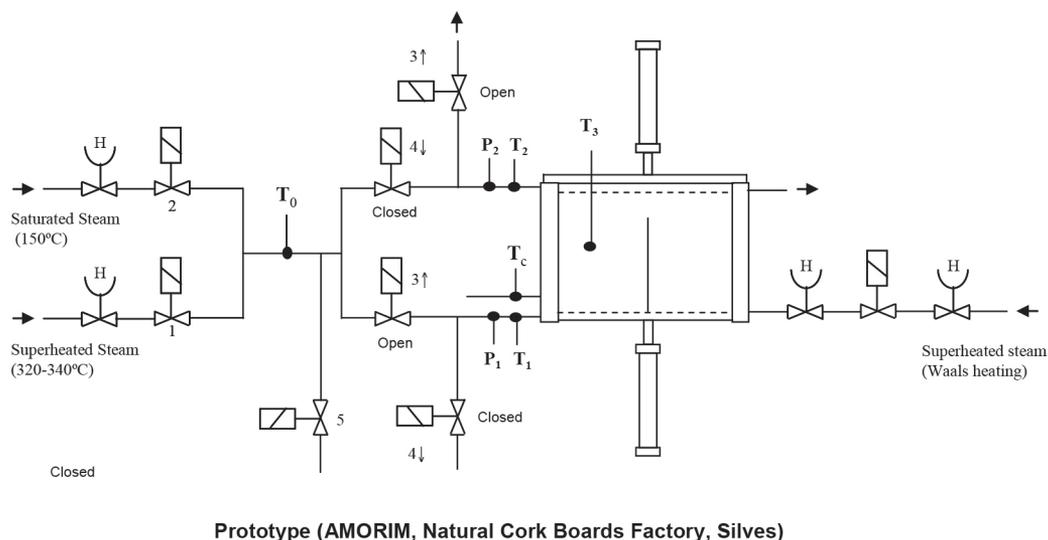

**Figure 1.** Autoclave used in the heat treatment in the absence of oxygen.

The autoclave (1 m<sup>2</sup> x 0.5 m in height), is divided into two parts by a metal plate placed vertically. The heating was achieved by superheated steam jacket as well as a mixture of superheated and saturated steam (Figure 1) from bottom to top. Since the experiments were made with a free autoclave volume, without any flow resistance, the steam rises vertically through the plate holes but with a preferentially horizontal direction from left to right with some projection against the wall on the right side, rising and moving then to the left.

Tests were performed at normal pressure and temperatures between 190°C and 210°C for 2, 6 and 12 h. It was not possible to test the samples at lower temperatures since the minimum working temperature for the autoclave was 190°C. The heating in the autoclave was done slowly up to 130°C through the sleeve and between 130°C and the working temperature the heating was quick and done with a mixture of saturated and superheated steam introduced inside the autoclave. The temperature of the treatment was maintained through the heating by the autoclave sleeve. The samples were taken from the autoclave after the treatment and placed in a desiccator. The mass loss was determined for each sample in relation to its initial dry mass as mentioned before.

For FTIR analysis, samples with approximately the same mass loss were chosen for both species and treatments. For each treatment, at least three samples were chosen, one with mass loss less than 1%, another one with mass loss around 3% which is generally considered the necessary mass loss to obtain a good stability, and a higher mass loss. For eucalypt treated in the autoclave a sample with mass loss less than 1% could not be obtained because all of the samples had a higher mass loss due to the treatment.

### **FTIR Analysis**

Treated and untreated samples were cut into small pieces and then ground separately in a knife mill Retsch SMI, followed by a Thomas mill. The crushed material was subject to a screening using a Retsch AS200basic with 40, 60 and 80 mesh sieves. The sieving was carried out during a period of 20 minutes at a speed of 50 rpm. The sample was separated into 4 fractions (>40, 40-60, 60-80 and <80 mesh). The samples from the 40-60 fraction were then extracted with dichloromethane, ethanol and water and air


dried, according to Tappi Standard (T 264 om-88). After that 200 mg of air-dried wood were weighted, placed in an oven at 60°C overnight. The next day the samples were ground in a ball mill (Mixer Mill MM2, Retsch) for 30 min at maximum power and left in a desiccator over phosphorus pentoxide. Heat treated pine and eucalypt wood samples with similar mass losses were chosen to collect the spectra. One spectrum was collected for each treatment-time-species combination.

The spectra were obtained with 1.50 to 1.55 mg of material with 200 mg of dry KBr ground in a ball mill (Mixer Mill MM2, Retsch) for 20 s. Disk (13 mm in diameter) were formed on a 10 tons load hydraulic press. The sample and reference spectra were obtained with 32 scans in a Bio-Rad FTS spectrometer 165 with a DTGS detector at 4  $\text{cm}^{-1}$  resolution for the 500-4000  $\text{cm}^{-1}$  range. As reference we used the empty sample compartment. The spectra were analysed with the program OPUS (Bruker), fixing the baseline on 20 points. No normalization was made since no band stayed unaltered throughout the treatment. To clarify some results the band height ratio between 1740 and 1650  $\text{cm}^{-1}$  was determined according to Faix and Böttcher (1992).


## RESULTS AND DISCUSSION

Figures 2 and 3 present the FTIR spectra of pine and eucalypt wood without treatment and after heat treatment in the oven. Eucalypt wood treated at 170°C for 2, 6, 12, and 24 h had mass losses of 0.1%, 1.1%, 2.7% and 3.7%, respectively. While pine wood treated at 180°C during 2, 6, 12, and 24 h had mass losses of 0.8%, 1.4%, 4.0% and 7.4%, respectively.


Figures 4 and 5 present the FTIR spectra of pine and eucalypt wood without treatment and after treatment in autoclave. Eucalypt wood treated at 190°C during 2 and 12 h had mass losses of 4.8% and 9.0% respectively. While pine wood treated at 190°C during 2 and 6 h and at 210°C during 12 h had mass losses of 0.4%, 3.5% and 13.2% respectively. In order to show more than one spectrum in each figure a shifting in the y axis was made.

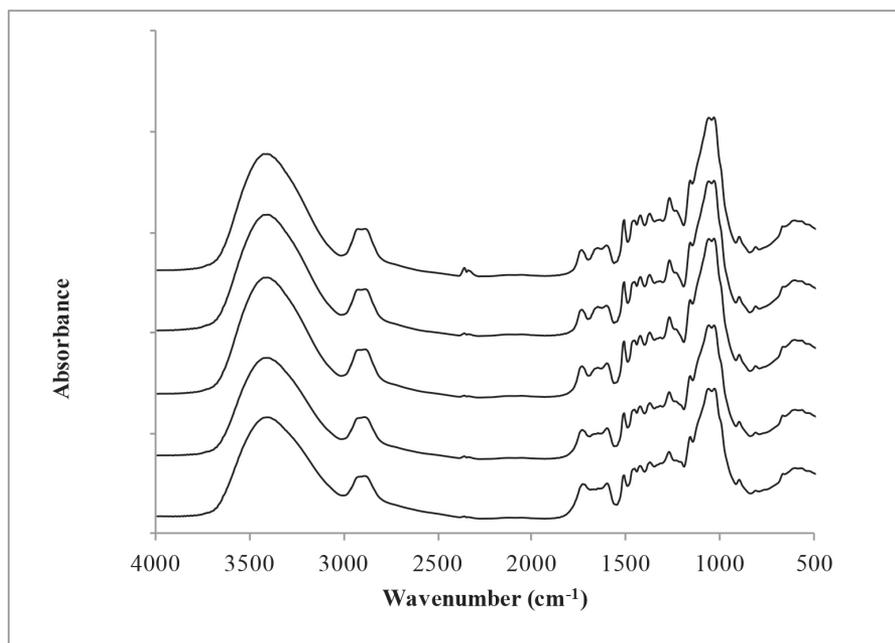


**Figure 2.** FTIR spectra of pine wood: from top to bottom without treatment initial and after treatment in an oven at 180°C for 2, 6, 12 and 24 h

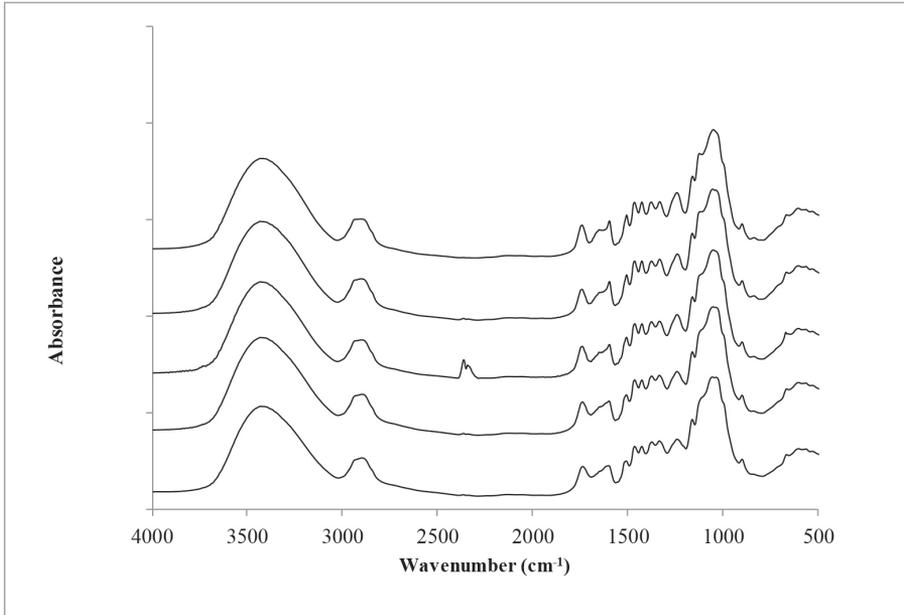

**Figure 3.** FTIR spectra of eucalypt wood: from top to bottom without treatment initial and after treatment in oven at 170°C for 2, 6, 12 and 24 h

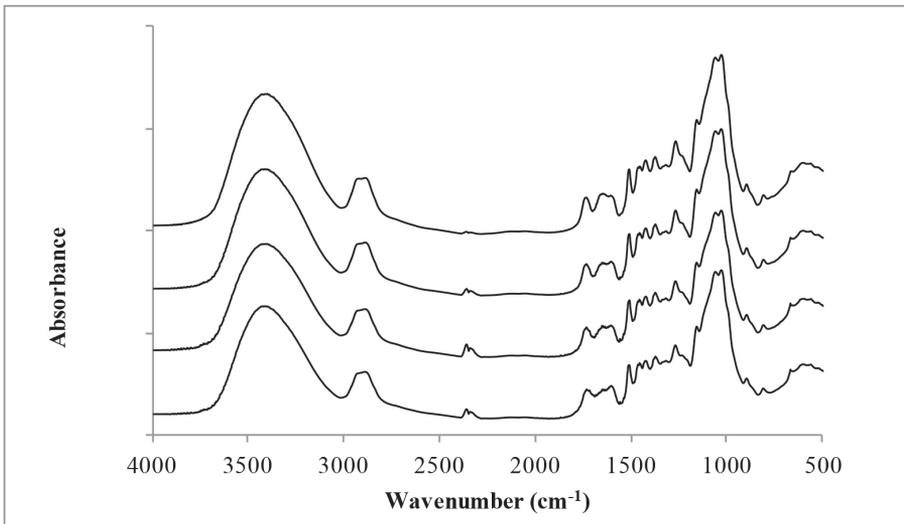

**Figure 4.** FTIR spectra of pine wood: from top to bottom without treatment initial and after treatment in autoclave at 190°C for 2, 6h, and at 210°C for 12 h

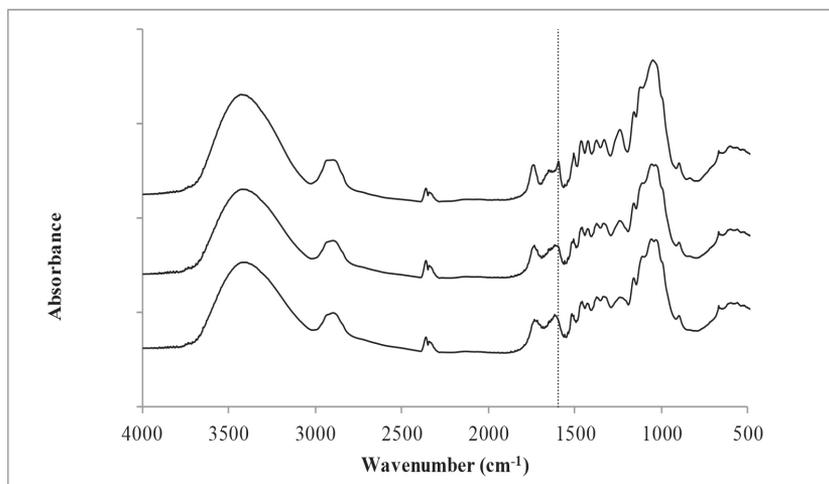

**Figure 5.** FTIR spectra of eucalyptus wood: from top to bottom without treatment initial and after treatment in autoclave at 190°C for 2 and 12h

Table 1 presents the most important bands that are observed in an infrared spectrum of wood and their assignment to functionality.

**Table 1.** Main bands of infrared spectrum of wood and their assignment to functionality

Wavenumber (cm <sup>-1</sup> )	Functionality	Vibrating type
3400	O-H of alcohols, phenols and acids	O-H stretching <sup>1,2</sup>
2970-2850	CH <sub>2</sub> , CH- and CH <sub>3</sub>	C-H stretching <sup>1,2</sup>
1750-1720	C=O of esters, ketones, aldehydes and acids	C=O stretching, non-conjugated <sup>1,2</sup>
1700-1550	Conjugated C=O and C=C	Conjugated C = O stretching, and C=C stretching <sup>1,2</sup>
1600	Aromatic ring	Benzene ring stretching vibrations <sup>1,2</sup>
1515-1500	Aromatic ring	Benzene ring stretching vibrations <sup>1,2</sup>
1460	CH	C-H deformations <sup>2</sup>
1420	Aromatic ring and CH	Benzene skeletal combined with C-H deformations <sup>1,2</sup>
1240-1330	Lignin S and G units and OH	C-O stretching and bending OH <sup>1,2</sup> antisymmetric stretching vibration of the acetyl ester groups
1140	G- Guaiacyl lignin and C-O	C-H deformations in G lignin and C-O stretching <sup>3</sup>
1128	S- Syringyl lignin and C-O	C-H deformations in S lignin and C-O stretching <sup>1,3</sup>
1025-1035	C-O-C	Deformation <sup>1,2</sup>
897	anti-symmetric out-of-phase stretching in pyranose ring	stretching in pyranose ring <sup>1,2</sup>

<sup>1</sup>Rodrigues *et al.* (1998), <sup>2</sup>Mitchell and Higgins (2002), <sup>3</sup>Faix (1991)

The differences between spectra from untreated and heat treated wood were difficult to interpret since there are several reactions occurring at the same time. Nevertheless, there were changes in the FTIR spectra of wood with the heating treatments even for the mildest conditions corresponding to small mass losses, as can be seen in the spectrum of eucalypt treated in oven (Figure 3) at 170°C during 2 h, corresponding to 0.1% mass loss. Even though there are not significant changes from untreated wood a small decrease of the 1740  $\text{cm}^{-1}$  peak was noticeable. With an increase in mass loss all of the wood compounds were affected leading to several changes in the spectrum.

It is a well known fact that chemical changes due to heat treatment start by deacetylation followed by depolymerization catalysed by the released acetic acid (Tjeerdsma et al 1998, Sivonen *et al.* 2002, Nuopponen *et al.* 2004). At the same time there is a carbohydrate dehydration that reduces accessible OH groups (Weiland and Guyonnet 2003) and leading to the formation of furfural and hydroxymethylfurfural (Tjeerdsma and Militz 2005). Lignin bonds are cleaved, resulting in a higher concentration of phenolic groups (Kollmann and Fengel 1965). The increased reactivity leads to lignin autocondensation and condensation reactions with aldehydes.


The FTIR spectra of heat-treated pine and eucalypt wood (Figures 2-5) showed a broadening to lower wavenumbers of the band at 3430  $\text{cm}^{-1}$  corresponding to the O-H stretching vibration from alcohols (3600-3300  $\text{cm}^{-1}$ ) and carboxylic acids (3300-2500  $\text{cm}^{-1}$ ), present either in polysaccharides and lignin. We suggest that this broadening might be due to the increase in carboxylic acids due to primary OH oxidation and/or hydrolysis of acetyl groups from hemicelluloses. Moreover the change of O-H stretching frequencies can also be due to the modification of cellulose crystallinity influenced by dehydration effects (Moharram and Mahmoud 2008, Spiridon *et al.* 2011). Even though O-H stretch due to polysaccharides should decrease, at the same time O-H from phenolic groups in lignin increases since it is a well known fact that the lignin percentage increases due to carbohydrate degradation (Esteves *et al.* 2011).

The two bands at 2900-2800  $\text{cm}^{-1}$  are composed by the overlapping of the stretch asymmetric vibrations of  $-\text{CH}_2-$  (generally around 2935-2915  $\text{cm}^{-1}$ ) and  $-\text{CH}_3$  (2970-2950  $\text{cm}^{-1}$ ) and by the overlapping of stretch symmetric vibrations of  $-\text{CH}_2-$  (2865-2845  $\text{cm}^{-1}$ ) and  $-\text{CH}_3$  (2880-2860  $\text{cm}^{-1}$ ). Normally the asymmetric band presents a higher absorptivity. The apparent shift in frequency for the maximum of CH band is due to structural and relative composition changes, namely changes at cellulose crystallinity level which influences the C-H and O-H stretch frequencies (Moharram and Mahmoud 2008, Spiridon *et al.* 2011), and changes in the relative importance of lignin methoxyl groups for which the  $\text{CH}_3$  stretching vibrations have lower CH stretching frequencies (Coates 2000). If the  $\text{OCH}_3$  increases by reduction of the carbohydrates this implies that the contribution of the  $\text{OCH}_3$  becomes larger and the consequence is that we can see that the right shoulder becomes maximum. Although the asymmetric/symmetric stretch of methylene group ( $-\text{CH}_2-$ ) appears at slightly lower wavelengths this does not necessary mean that there is an increase in methylene groups at the expense of methyl groups.

The C=O linkage exhibits strong absorptions in FTIR spectra between 1750 and 1700  $\text{cm}^{-1}$ , and the precise wavenumber depends of the functional group (carboxylic acid: at about 1725-1700  $\text{cm}^{-1}$ ; ester, ketone: 1725-1705  $\text{cm}^{-1}$ , aldehyde: 1740-1720  $\text{cm}^{-1}$ ) and of its structural location, with lower wavenumbers for conjugated C=O. According to Mitchell and Higgins (2002), the band around 1730  $\text{cm}^{-1}$  is almost exclusively due to the carbonyl groups of acetoxy groups in xylan. In the spectra of eucalypt and pine oven treated wood (Figures 2 and 3) this band decreased initially but for longer treatments the band increased, shifting to smaller wavenumbers. The decrease at the beginning of the heat treatment (with mass losses around 1%) might be due to the breaking of acetyl or acetoxy groups in xylan. Similar results were obtained by Tjeerdsma and Militz (2005) after the first hydrothermal step of the Plato process and by Kocaefe *et al.* (2008b) with wood treated by the Perdure process. In the spectra of wood treated in autoclave (Figures 4 and 5) there was no initial decrease but only an increase and shifting to about 1730  $\text{cm}^{-1}$ . A possible reason for the absence of the initial decrease in these spectra is that the smaller mass losses for autoclave heat treated wood are around 4-5 % and the cleavage of acetyl groups had

already occurred, possible around 1-2% mass loss. At these mass losses (4-5%) the decrease can no longer be seen because another effect superimposes. The increase and shifting for smaller wavenumbers with increasing treatment severity may be due to an increase of carbonyl or carboxyl groups in lignin or carbohydrates by oxidation. This increase was also obtained by Kotilainen *et al.* (2000) with *Pinus sylvestris* and *Picea abies* and González-Peña *et al.* (2009) who attributed this increase to lignin condensation reactions at the expense of C=C double bonds in conjugated carbonyl groups in lignin, vibrating at  $1654\text{ cm}^{-1}$ . Tjeerdsma and Militz (2005), who studied the FTIR spectra of holocellulose and lignin of heat-treated *Fagus sylvatica* and *Pinus sylvestris*, concluded that the increase of the  $1740\text{ cm}^{-1}$  band was due only to the lignin as there was no increase in holocellulose. These authors considered this increase to be due to the occurrence of esterification when the existent acid reacts with the hydroxyl groups of the cell-wall material. If esterification occurs the band at  $1240\text{ cm}^{-1}$  should also increase due to antisymmetric stretching vibration of the acetyl ester groups which with our samples does not happen. Nevertheless since this is a composed band the eventual increase could be overlapped by the decrease of other compound. Li *et al.* (2002) studied the heat degradation of lignin in hardwood and softwood and obtained an increase in the peak at  $1720\text{ cm}^{-1}$  with increasing temperature, which they concluded to be due to the production of C=O bonds in lignin.

To better understand what happens between  $1800$  and  $1600\text{ cm}^{-1}$  wavenumber Figure 6 shows this range of figure 2 in detail (pine oven treated wood) and presents also the ratio of the band heights at  $1740$  and  $1650\text{ cm}^{-1}$ . In this figure an initial decrease followed by an increase of the  $1740\text{ cm}^{-1}$  band in relation to  $1650\text{ cm}^{-1}$  band can be seen. The maximum of the  $1740\text{ cm}^{-1}$  band shifts from the initial point around  $1738\text{ cm}^{-1}$  to about  $1729\text{ cm}^{-1}$ .

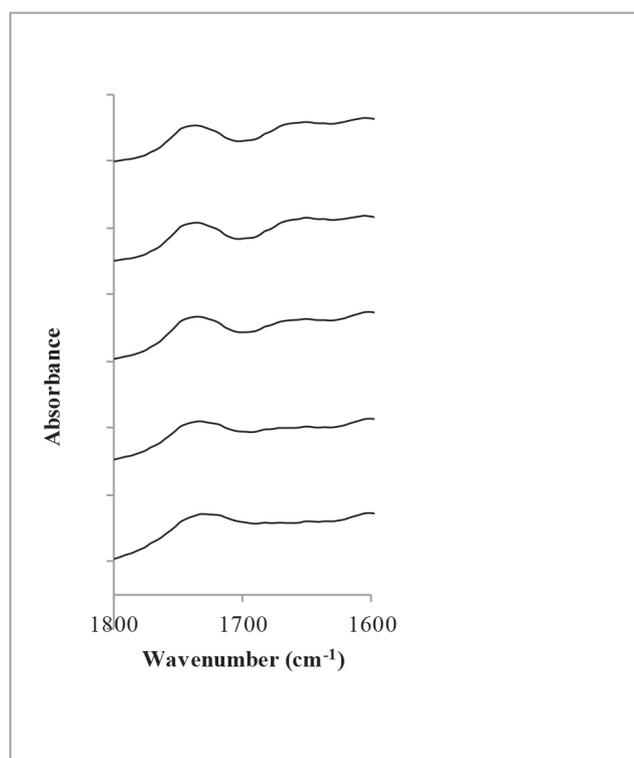


**Figure 6.** FTIR spectra of pine wood in the wavenumber range from  $1800$  to  $1600\text{ cm}^{-1}$ . From top to bottom: without treatment and after treatment in an oven at  $170^{\circ}\text{C}$  for 2, 6, 12 and 24 h and ratio of band heights at  $1740\text{ cm}^{-1} / 1650\text{ cm}^{-1}$ .

The increase of the peak at  $1740\text{ cm}^{-1}$  in relation to  $1650\text{ cm}^{-1}$  means that non-conjugated C=O groups increased in relation to conjugated groups. Similar results were described by González-Peña *et al.* 2009.

The band at  $1595\text{ cm}^{-1}$  corresponds to vibrations in the aromatic ring of lignin plus C=O stretching. The band at  $1595\text{ cm}^{-1}$  broadens to about  $1613\text{ cm}^{-1}$  for eucalypt but not for pine wood (Figures 2 to 5). This peak broadening suggests that there was an increase of structural diversity around the aromatic rings, absorbing at a greater range of frequencies. The height of the band seemed to increase only in the spectrum of eucalypt wood treated in autoclave (Figure 5). According to Kotilainen *et al.* (2000) this band increases due to an increase in the percentage of lignin in treated wood. Li *et al.* (2002) also obtained an increase of the peak at  $1595\text{ cm}^{-1}$  in lignin at temperatures between  $25^{\circ}\text{C}$  and  $460^{\circ}\text{C}$ , although no explanation was given.

Aromatic rings exhibit, most of the times, a characteristic band at approximately  $1500\text{ cm}^{-1}$ , corresponding to benzene ring stretching vibrations. This band is very important because it is at about  $1505\text{ cm}^{-1}$  for hardwood lignin (Guaiacyl - G and Syringyl - S) and at about  $1510\text{ cm}^{-1}$  for softwood lignin (Guaiacyl-G) (Faix 1991). The band at  $1505\text{ cm}^{-1}$  for eucalypt wood decreased, shifting to about  $1512\text{ cm}^{-1}$  (Figure 7). This can be due to the decrease of the methoxyl groups in lignin which would lead to a lignin more similar to softwood (G-lignin) or to the loss of S units, since this monomer is generally less condensed by C-C bonds than guaiacyl monomers and is more prone to be liberated by a thermal degradation (Faix *et al.* 1990).

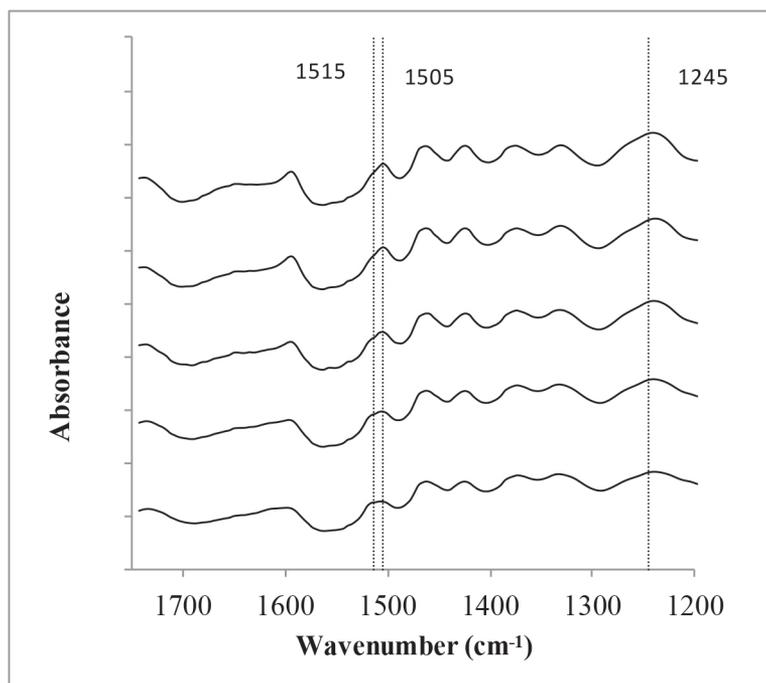

**Figure 7.** FTIR spectra of eucalypt wood from top to bottom without treatment and after treatment in oven at  $170^{\circ}\text{C}$  for 2, 6, 12 and 24 h in the range  $1750\text{-}1200\text{ cm}^{-1}$

The shifting of this band is in agreement to the results presented by Windeisen *et al.* (2007) and Kocaefe *et al.* (2008b), and attributed to the breaking of aliphatic side-chains in lignin and/or condensation reactions.

The band at 1460  $\text{cm}^{-1}$  corresponds to the asymmetric deformation of C-H bond of xylan, while the band at 1420  $\text{cm}^{-1}$  corresponds to the vibration of the aromatic ring of lignin, but also to the C-H bending in cellulose (Mitchell and Higgins 2002). No consistent variation was found for the 1460  $\text{cm}^{-1}$  and 1420  $\text{cm}^{-1}$  peak. According to Kotilainen *et al.* (2000) and Weiland and Guyonnet (2003) the peaks at 1460  $\text{cm}^{-1}$  and 1420  $\text{cm}^{-1}$  increase with heat treatment. The band at 1375  $\text{cm}^{-1}$  broadened to smaller wavenumbers but with no consistent variance. The band at 1333  $\text{cm}^{-1}$  represents the contributions of all structural components of wood because it corresponds to C-H bending of polysaccharides which joins the band at 1327  $\text{cm}^{-1}$  of S and G lignin condensed units (Faix 1991). There was a clear increase at 1330  $\text{cm}^{-1}$  corresponding to an increase in lignin condensation. The same was reported by Windeisen *et al.* (2007).

For eucalypt wood (Figures 3, 5 and 7) the band at 1245  $\text{cm}^{-1}$ , decreased in height but broadened which once again confirms the existence of a more condensed structure (Windeisen *et al.* 2007, Kocaefe *et al.* 2008b). According to Kotilainen *et al.* (2000) this peak increases, but no explanation was given. The band at 1140  $\text{cm}^{-1}$  is the result of the sum of the contribution of C-H deformation in aromatic rings and C-O stretching in primary alcohols. This band has a shoulder at 1140  $\text{cm}^{-1}$  in woods with G lignin (Figure 2 and 4) and 1128  $\text{cm}^{-1}$  in the woods with GS lignin (Figures 3 and 5) (Faix 1991). No consistent variation was found for this band.

The peak at 897  $\text{cm}^{-1}$ , corresponding to the sugar ring tension, seemed to decrease with increasing severity of the treatment which is consistent with ring opening (Figures 2 to 5). Similar results were obtained by Kotilainen *et al.* (2000) and González-Peña *et al.* (2009).

These results are generally consistent with the chemical changes determined by wet chemistry for heat treated pine and eucalypt in oven and in autoclave (Esteves *et al.* 2006, Esteves *et al.* 2008b, Esteves *et al.* 2011). In the beginning of the treatment, hemicelluloses are the first to degrade, as proved here by the initial decrease of the 1740  $\text{cm}^{-1}$  peak attributed to the cleavage of acetyl or acetoxy groups in xylan. The attack on polysaccharides during heating is clear by the decrease of the peak at 897  $\text{cm}^{-1}$  corresponding to the pyranose ring opening. The increase in lignin content that derived from the carbohydrate loss can be seen by the later increase of the 1740  $\text{cm}^{-1}$  peak which according to Li *et al.* (2002) is due to the formation of carbonyl groups in lignin.

No significant differences between oven and autoclave treatments were observed. In the range of the studied thermal treatments and wood mass losses, no influence of air or steam heating was detected by FTIR analysis. The different chemical reactions occurring at the same time make the existing differences between spectra very difficult to follow.

## CONCLUSIONS

The heat treatment caused significant changes in the chemical composition and structure of wood, by changing polysaccharides and lignin. That can be observed by FTIR analysis. Hemicelluloses are the first components to degrade due to deacetylation. Hardwood lignin changes more than softwood lignin, due to demethoxylation, loss of S units or breaking of aliphatic side-chains. The macromolecular lignin structure becomes more condensed with the presence of non-conjugated/conjugated groups. The changes induced by the thermal treatment are due to different chemical reactions occurring simultaneously.

## ACKNOWLEDGEMENTS

The authors thank the Portuguese Foundation for Science and Technology and the Centre for Studies in Education, Technologies and Health for the financial support.

## REFERENCES

- Bekhta, P.; Niemz, P. 2003.** Effect of high temperature on the change in color, dimensional Stability and mechanical properties of spruce wood. *Holzforschung* 57(5): 539-546.
- Coates, J. 2000.** *Interpretation of Infrared Spectra, A Practical Approach in Encyclopedia of Analytical Chemistry*. R.A. Meyers (Ed.). John Wiley & Sons Ltd. pp. 10815-10837
- Dirol, D.; Guyonnet, R. 1993.** Durability by rectification process. In: *International Research Group Wood Pre*, Section 4-Processes, N° IRG/WP 93-40015.
- Esteves, B.; 2006.** *Technological Improvement of Portuguese Woods by Heat Modification*. Ph.D. Thesis in Environmental Engineering. School of Agronomy. Technical University of Lisbon. In Portuguese. 289p
- Esteves, B.; Domingos, I.; Pereira, H. 2007a.** Improvement of technological quality of eucalypt wood by heat treatment in air at 170-200°C. *Forest Prod J* 57 (1-2): 47-52.
- Esteves, B.; Velez Marques, A.; Domingos, I.; Pereira, H. 2007b.** Influence of steam heating on the properties of pine (*Pinus pinaster*) and eucalypt (*Eucalyptus globulus*) wood. *Wood Sci Technol* 41(3):193-207.
- Esteves, B. M.; Domingos, I. J.; Pereira, H. M. 2008a.** Pine wood modification by heat treatment in air. *Bioresources* 3(1): 142-154.
- Esteves, B.; Graça, J.; Pereira, H. 2008b.** Extractive composition and summative chemical analysis of thermally treated eucalypt wood. *Holzforschung* 62(3):344-351.
- Esteves, B.; Velez Marques, A.; Domingos, I.; Pereira, H. 2008c.** Heat induced colour changes of pine (*Pinus pinaster*) and eucalypt (*Eucalyptus globulus*) wood. *Wood Sci Technol* 42(5): 369-384.

**Esteves, B.; Videira, R.; Pereira, H. 2011.** Chemistry and ecotoxicity of heat treated pine wood extractives, *Wood Sci Technol* 45 (6 ):661-676.

**Faix, O. 1991.** Classification of lignins from different botanical origins by FT-IR spectroscopy. *Holzforschung* 45 (1): 21-27.

**Faix, O. Böttcher, J. 1992.** The influence of particle size and concentration in transmission and diffuse reflectance spectroscopy of wood. *Holz als Roh- und Werkst* 50(6): 221-226.

**Faix, O.; Meier, D.; Fortmann, I. 1990.** Thermal-degradation products of wood. Gas chromatographic separation and mass spectrometric characterization of monomeric lignin derived products. *Holz als Roh- und Werkst* 48(7-8 ):281-285.

**González-Peña, M.M.; Curling, S.F.; Hale, M.D.C. 2009.** On the effect of heat on the chemical composition and dimensions of thermally-modified wood. *Polymer Degradation and Stability* 94(12): 2184-2193.

**Jämsä, S.; Viitaniemi, P. 2001.** Heat treatment of wood- Better durability without chemicals. In: *Proceedings of special seminar held in Antibes, France, city, 68p.*

**Moharram, M.; Mahmoud, O. 2008.** FTIR Spectroscopic Study of the Effect of Microwave Heating on the Transformation of Cellulose I into Cellulose II during Mercerization. *Journal of Applied Polymer Science* 107(1): 30-36.

**Kamdem, D.; Pizzi, A.; Jermannaud, A. 2002.** Durability of heat-treated wood. *Holz Roh-Werkst* 60(1): 1-6.

**Kocaefe, D.; Jun, L. S.; Yang, D.Q.; Bouazara, M. 2008a.** Mechanical properties, dimensional stability, and mold resistance of heat-treated jack pine and aspen. *Forest Prod J* 58(6):88-93

**Kocaefe, D.; Poncsak, S.; Boluk, Y. 2008b.** Effect of thermal treatment on the chemical composition and mechanical properties of birch and aspen. *Bioresources* 3(2): 517-537.

**Kollmann, F.; Fengel, D. 1965.** Changes in the Chemical composition of Wood by Thermal Treatment. *Holz als Roh und Werkst* 12 (12): 461-468.

**Kotilainen, R.; Toivannen, T.; Alén, R. 2000.** FTIR monitoring of chemical changes in softwood during heating. *Journal of Wood Chemistry and Technology* 20(3): 307-320.

**Li, J.; Li, B.; Zhang, X. 2002.** Comparative studies of heat degradation between larch lignin and Manchurian ash lignin. *Polymer Degradation and Stability* 78: 279-285.

**Michell, A.; Higgins, H. 2002.** *Infrared Spectroscopy in Australian Forest Products research.* CSIRO Forestry and Forest Products, Melbourne, Australia 60p.

**Michell, A.; Watson A.; Higgins H. 1965.** An infrared spectroscopic study of delignification of *Eucalyptus regnans*. *Tappi* 48: 520-532.

**Mitsui, K.; Takada, H., Sugiyama, M.; Hasegawa, R. 2001.** Changes in the properties of light-irradiated wood with heat treatment: Part 1 Effect of treatment conditions on the change in color. *Holzforschung* 55(6): 601-605.

**Nuopponen, M.; Vuorinen, T.; Jamsä, S.; Viitaniemi, P. 2004.** Thermal modifications in softwood studied by FT-IR and UV resonance Raman spectroscopies. *J Wood Chem Technol* 24(1): 13-26.

**Rodrigues, J.; Faix O.; Pereira H. 1998.** Determination of lignin content of *Eucalyptus globulus* wood using FTIR spectroscopy. *Holzforschung* 52(1): 46-50.

**Sailer, M.; Rapp, A.; Leithoff, H. 2000.** Improved resistance of Scots pine and spruce by application of an oil-heat treatment. In: *International Research Group Wood Pre*, Section 4-Processes, N° IRG/WP 00-40162.

**Spiridon, I.; Teacă, C.; Bodîrlău, R. 2011.** Structural changes evidenced by FTIR spectroscopy in cellulosic materials after pre-treatment with ionic liquid and enzymatic hydrolysis. *Bioresources* 6(1):400-413.

**Sivonen, H.; Maunu, S.; Sundholm, F.; Jämsä, S.; Viitaniemi, P. 2002.** Magnetic resonance studies of thermally modified wood. *Holzforschung* 56(6): 648-654.

**TAPPI Test Method. 1988.** Preparation of Wood for Chemical Analysis. T264 om-88. In Tappi Test Methods. Atlanta, GA: Technical Association of the Pulp and Paper Industry.

**Tjeerdsma, B.; Boonstra, M.; Pizzi, A.; Tekely, P.; Militz, H. 1998.** Characterisation of thermally modified wood: Molecular reasons for wood performance improvement. *Holz Roh-Werkst* 56(3): 149-153.

**Tjeerdsma, B.; Militz, H. 2005.** Chemical changes in hydrothermal treated wood: FTIR analysis of combined hydrothermal and dry heat-treated wood. *Holz als Roh- und Werkst* 63(2): 102-111.

**Unsal, O.; Ayrilmis, N. 2005.** Variations in compression strength and surface roughness of heat-treated Turkish river red gum, *J Wood Sci* 51(4): 405-409.

**Viitanen, H.; Jämsä, S., Paajanen, L.; Nurmi, A.; Viitaniemi, P. 1994.** The effect of heat treatment on the properties of spruce. *IRG/WP 94-40032*, 4p

**Viitaniemi, P.; Jämsä, S.; Viitanen, H.; 1997.** *Method for improving biodegradation resistance and dimensional stability of cellulosic products.* United States Patent N° 5678324 (US005678324). <http://www.freepatentsonline.com/5678324.html>

**Wang, J.; Cooper, P. 2005.** Effect of oil type, temperature and time on moisture properties of hot oil-treated wood. *Holz Roh-Werkst* 63(6): 417-422

**Weiland, J.; Guyonnet, R. 2003.** Study of chemical modifications and fungi degradation of heatly modified wood using DRIFT spectroscopy. *Holz als Roh und Werkst* 61(3): 216-220.

**Windeisen, E.; Strobel, C.; Wegener, G. 2007.** Chemical changes during the production of thermo-treated beech wood. *Wood Sci Technol* 41(6): 523-536.

**Yildiz, S. 2002.** Physical, mechanical, technological and chemical properties of beech and spruce wood treated by heating. PhD dissertation, Karadeniz Tech. Univ.; Trabzon, Turkey. 200p